

OȚELURI PENTRU LUCRU LA RECE

Application Segments

Muncă la rece

Available Product Variants

Long Products*

Plates

* Datele prezentate se referă exclusiv la produsele lungi. Vă rugăm să respectați explicațiile detaliate de la sfârșitul fișei tehnice (pdf).

Product Description

BÖHLER K390 MICROCLEAN is a high-alloyed, high-performance cold work tool steel manufactured using powder metallurgy. This material has the highest alloy content in the group of cold work tool steels with high vanadium content. The high alloy content gives this material outstanding wear resistance. At the same time, the powder metallurgical manufacturing process creates a uniform matrix with finely distributed primary carbides. Among other things, this leads to good material toughness. BÖHLER K390 MICROCLEAN is a problem solver for applications requiring extremely high wear resistance and compressive strength.

Process Melting

Metalurgia pulberilor

Properties

- > Rezistență și ductilitate : high
- > Rezistență la uzură : very high
- > Rezistența la compresiune : very high
- > Stabilitatea dimensională : very high

Applications

- > Cuțit de mașină (pentru producători)
- > Montarea monedei
- > Șuruburi și butoaie
- > Componente pentru construcții subterane (foraje, puțuri etc.)
- > Materiale plastice ranforsate cu fibră de sticlă
- > Mineral Processing
- > Cold Rolling incl. Sendzimir Rolls
- > Laminare
- > Blanking fin, ștanțare, blanking
- > Rularea firelor
- > Componente pentru industria reciclării
- > Cuțite industriale
- > Drilling
- > Industria ambalajelor
- > Formare la rece
- > Pulbere de presare
- > Rulouri
- > Matrite de perforare a pastilelor
- > Wear Applications
- > Roll Forming

Chemical composition (wt. %)

C	Si	Mn	Cr	Mo	V	W	Co
2.47	0.55	0.40	4.20	3.80	9.00	1.00	2.00

Material characteristics

	Compressive strength	Dimensional stability during heat treatment	Toughness	Wear resistance abrasive	Wear resistance adhesive
BÖHLER K390 MICROCLEAN	★★★★★	★★★★★	★★★★★	★★★★★	★★★★★
BÖHLER K100	★★	★★	★	★★★	★★
BÖHLER K105	★★	★★	★	★★	★★
BÖHLER K107	★★	★★	★	★★★	★★
BÖHLER K110	★★	★★★	★	★★★	★★
BÖHLER K190 MICROCLEAN	★★★★★	★★★★★	★★★★★	★★★★★	★★★★★
BÖHLER K294 MICROCLEAN	★★★★★	★★★★★	★★★	★★★★★	★★★★★
BÖHLER K340 ECOSTAR	★★★	★★★	★★	★★	★★
BÖHLER K340 ISODUR	★★★	★★★★★	★★★	★★★	★★★★★
BÖHLER K346	★★★	★★★	★★★	★★★★★	★★
BÖHLER K353	★★	★★★	★★	★★	★★
BÖHLER K360 ISODUR	★★★	★★★★★	★★★	★★★★★	★★★★★
BÖHLER K490 MICROCLEAN	★★★★★	★★★★★	★★★★★	★★★★★	★★★★★
BÖHLER K497 MICROCLEAN	★★★★★	★★★★★	★★★	★★★★★	★★★★★
BÖHLER K888 MATRIX	★★★★★	★★★★★	★★★★★	★★	★★
BÖHLER K890 MICROCLEAN	★★★★★	★★★★★	★★★★★	★★★	★★★


Delivery condition

Recoaptă	
Hardness (HB)	max. 280

Heat treatment

Eliminarea stresului		
Temperature	650 to 700 °C	After through heating, hold in neutral atmosphere for 1-2 hours. Slow cooling in furnace Intended to relieve stresses caused by extensive machining or in complex shapes.
Călire și revenire		
Temperature	1,030 to 1,180 °C	Quenching: Oil, gas (N ₂). Holding time after temperature equalization: 20 to 30 minutes (hardening temperature 1030 - 1150 °C 1886 - 2102 °F) and 10 min (hardening temperature 1180 °C 2156 °F) Low hardening temperature for high toughness. High hardening temperature for high wear resistance. After hardening, tempering to the desired working hardness according to the tempering chart.

Tempering chart

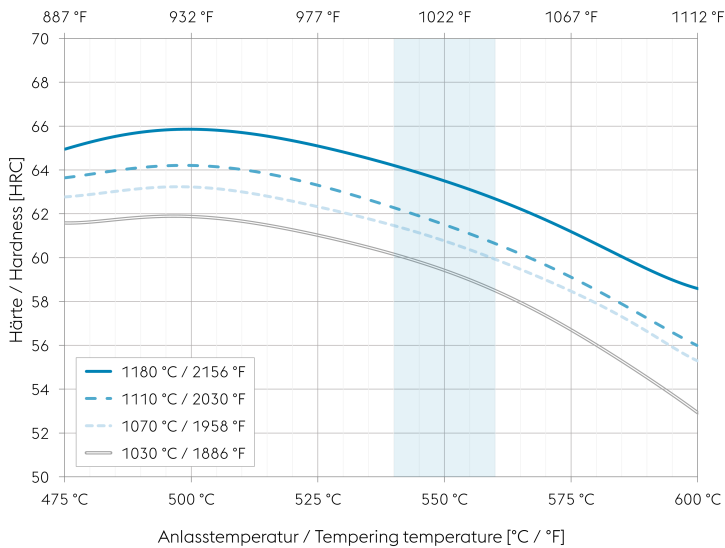

Specimen size: square 20 mm (0,787 inch)

Slow heating to tempering temperature immediately after hardening.

Time in furnace 1 hour for each 20 mm (0,787 inch) of workpiece thickness but at least 2 hours.

Please refer to the tempering chart for guide values for the achievable hardness after tempering.


It is recommended to temper at least three times above the secondary hardness maximum.

Cooling in air to room temperature after each tempering step is recommended.

Tempering for stress relieving 30 to 50 °C (86 to 122 °F) below the highest tempering temperature.

Recommended tempering temperature range is indicated by the blue area in the chart.

Continuous cooling CCT curves

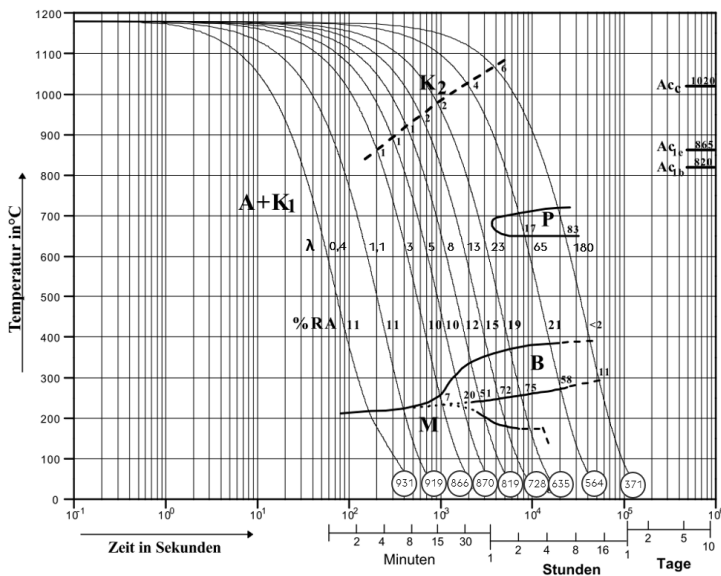

Austenitising temperature: 1180 °C (2155 °F)
Holding time: 5 minutes


○ Vickers hardness

1...83 phase percentages

0.4...180 cooling parameter λ , i.e. duration of cooling from 800 to 500 °C (1472 to 932 °F) in $s \times 10^{-2}$

A... Austenite
K... Carbide
P... Pearlite
B... Bainite
M... Martensite

Quantitative phase diagram

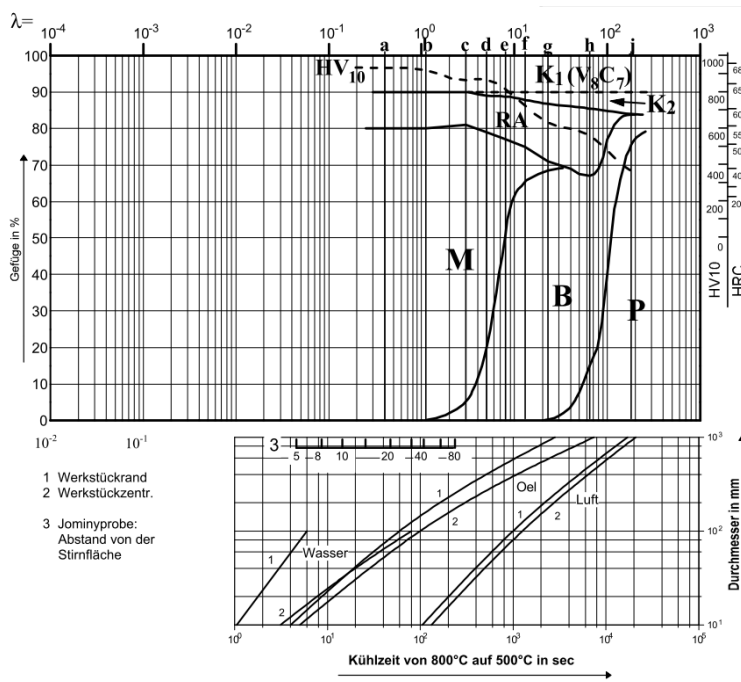

HV10... Vickers Hardness
K... Carbide
RA... Residual austenite
M... Martensite
B... Bainite
P... Pearlite

1... Edge or face
2... Core
3... Jominy test: distance from the quenched end

Physical Properties

Temperature (°C)	20
Density (kg/dm ³)	7.6
Thermal conductivity (W/(m.K))	21.5
Specific heat (kJ/kg K)	0.464
Spec. electrical resistance (Ohm.mm ² /m)	0.59
Modulus of elasticity (10 ³ N/mm ²)	220

Thermal Expansions between 20°C | 68°F and ...

Temperature (°C)	100	200	300	400	500	600
Thermal expansion (10 ⁻⁶ m/(m.K))	10.3	10.67	11.03	11.38	11.7	11.97

If other available product variants are listed in addition to long products, please note that these may differ in terms of melting process, technical data, delivery and surface condition as well as available product dimensions. For mandatory technical specifications, other requirements and dimensions, please contact our regional voestalpine BÖHLER sales companies. The data contained in this brochure is merely for general information and therefore shall not be binding on the company. We may be bound only through a contract explicitly stipulating such data as binding. Measurement data are laboratory values and can deviate from practical analyses. The manufacture of our products does not involve the use of substances detrimental to health or to the ozone layer.

voestalpine BÖHLER Edelstahl GmbH & Co KG
 Mariazeller Straße 25
 8605 Kapfenberg, AT
 T. +43/50304/20-0
 E. info@bohler-edelstahl.at
<https://www.voestalpine.com/bohler-edelstahl/de/>