

OȚELURI PENTRU SCULE PENTRU LUCRU LA CALD

Application Segments

Lucrări la cald

Available Product Variants

Long Products*

Open Die Forgings

* Datele prezentate se referă exclusiv la produsele lungi. Vă rugăm să respectați explicațiile detaliate de la sfârșitul fișei tehnice (pdf).

Product Description

BÖHLER W303 ISODISC is a 5% chromium steel and corresponds to material number 1.2367 (X38CrMoV5-3). This tool steel has good hot toughness as well as a very high hot hardness and resistance against heat-checkings. Compared to an X37CrMoV5-1 (material number 1.2343), the steel has an increased molybdenum content, which significantly increases its thermal resistance and thus makes it the ideal material in die closed-die forging, open-die forging and extrusion.

Process Melting

Aer topit

Properties

- > Rezistență și ductilitate : good
- > Rezistență la uzură : high
- > Machinability : very high
- > Duritate la cald (duritate roșie) : high
- > Poluabilitate : good
- > Conductivitate termică : good
- > Micro-curățenie : good

Applications

- > Extrudare
- > Turnare sub presiune înaltă
- > Inginerie mecanică
- > Forjare (la cald / semi-cald)
- > Întărire prin presare / ștampilare la cald
- > Gravitate / presiune scăzută turnare sub presiune
- > Forjare progresivă (Hatebur)

Technical data

| Material designation | | Standards | |
|----------------------|-----|-----------|--------|
| 1.2367 | SEL | 4957 | EN ISO |
| X38CrMoV5-3 | EN | | |

Chemical composition (wt. %)

| C | Si | Mn | Cr | Mo | V |
|------|------|------|------|------|------|
| 0.38 | 0.40 | 0.40 | 5.00 | 2.80 | 0.55 |

Material characteristics

| | High temperature strength | High temperature toughness | High temperature wear resistance | Machinability in as supplied condition | Polishability |
|----------------------------|---------------------------|----------------------------|----------------------------------|----------------------------------------|---------------|
| BÖHLER W303 ISODISC | ★★★★★ | ★★★ | ★★★★★ | ★★★★★ | ★★★ |
| BÖHLER W300 ISODISC | ★★ | ★★★ | ★★ | ★★★★★ | ★★★ |
| BÖHLER W300 ISOBLOC | ★★ | ★★★★★ | ★★ | ★★★★★ | ★★★★★ |
| BÖHLER W302 ISODISC | ★★★ | ★★★ | ★★★ | ★★★★★ | ★★★ |
| BÖHLER W302 ISOBLOC | ★★★ | ★★★★★ | ★★★ | ★★★★★ | ★★★★★ |
| BÖHLER W320 ISODISC | ★★★ | ★★ | ★★★ | ★★★★★ | ★★★ |
| BÖHLER W350 ISOBLOC | ★★★ | ★★★★★ | ★★★ | ★★★★★ | ★★★★★ |
| BÖHLER W360 ISOBLOC | ★★★★★ | ★★★★★ | ★★★★★ | ★★★★★ | ★★★★★ |
| BÖHLER W400 VMR | ★★ | ★★★★★ | ★★ | ★★★★★ | ★★★★★ |
| BÖHLER W403 VMR | ★★★★★ | ★★★★★ | ★★★★★ | ★★★★★ | ★★★★★ |


Delivery condition

| Recoaptă | |
|-----------------------|----------|
| Hardness (HB) | max. 229 |
| Durificat și temperat | |
| Hardness (HRC) | 30 to 44 |


Heat treatment

| Recoacere | | |
|----------------------|-------------------|---------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------|
| Temperature | 750 to 800 °C | Holding time 6 to 8 hours. Slow, controlled furnace cooling at 10 to 20°C/h (50 to 68 °F/hr) to approx. 600°C (1112°F), further cooling in air. |
| Eliminarea stresului | | |
| Temperature | 600 to 670 °C | For stress relief after extensive machining or for complicated tools. Holding time depending on tool size after complete heating 2 - 6 hours in neutral atmosphere. Slow furnace cooling. |
| Călire și revenire | | |
| Temperature | 1,030 to 1,080 °C | Holding time after temperature equalization: 15 to 30 minutes; Quenching: Oil, salt bath (500 - 550°C [932-1022°F]), air, vacuum; After hardening, tempering to the desired working hardness (see tempering chart). |

Heat treatment sequence

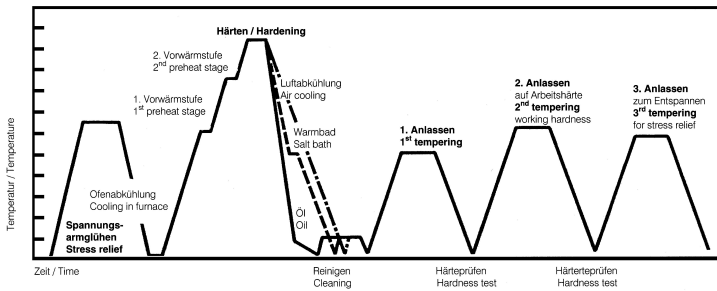


Continuous cooling CCT curves

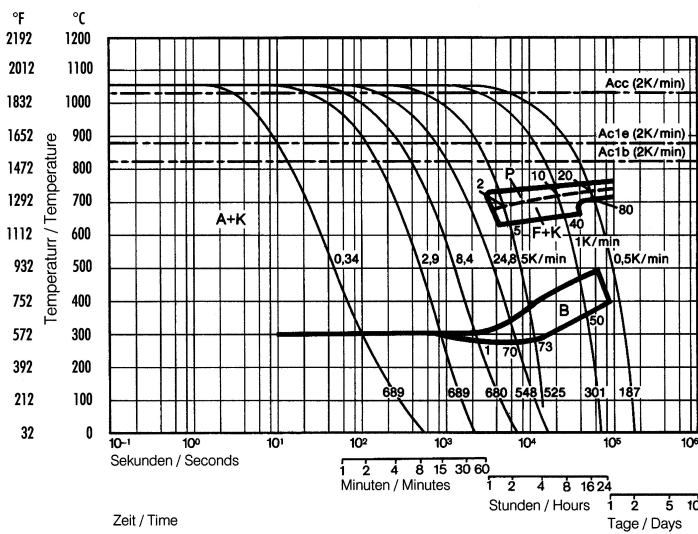

Austenitising temperature: 1922°F (1050°C)
Holding time: 15 minutes

689 - 187 Vickers hardness
1...80 phase percentages
0.34...24.8 cooling parameter, i.e. duration of cooling from 1472 - 932°F (800-500°C) in $s \times 10^{-2}$
41...32.9°F/min (5...0.5 K/min) cooling rate in °F/min (K/min) in the 1472 - 932°F (800-500°C) range

Quantitative phase diagram

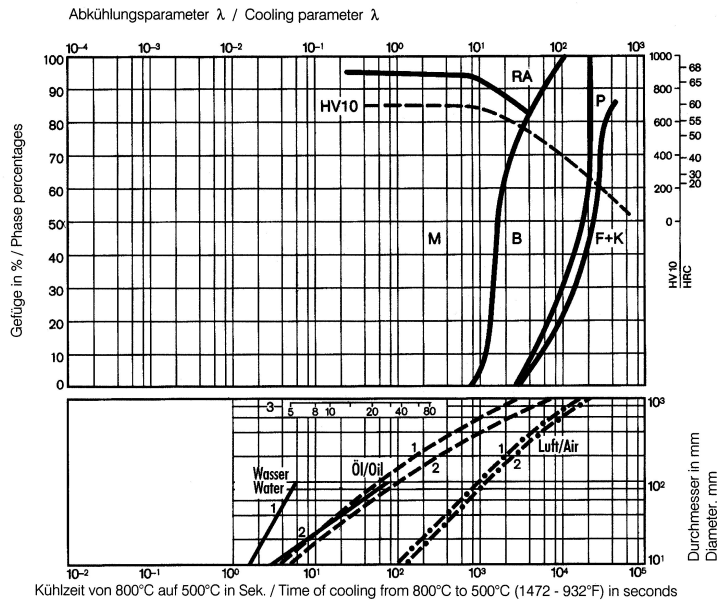


- A... Austenite
- B... Bainite
- F... Ferrite
- K... Carbide
- M... Martensite
- P... Perlite
- RA... Retained austenite

- Oil cooling
- · - Air cooling

- 1... Edge or face
- 2... Core
- 3... Jominy test: distance from end

Tempering chart

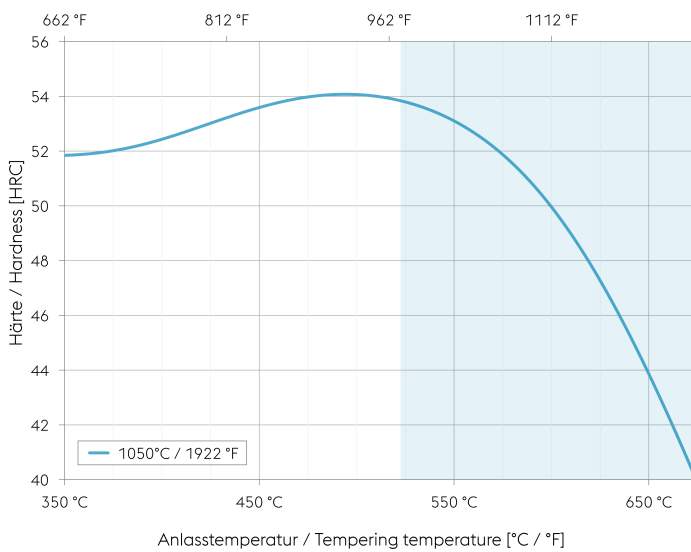

Tempering:

Slow heating to tempering temperature immediately after hardening / time in furnace 1 hour for each 0,787 inch (20 mm) of work piece thickness but at least 2 hours / cooling in air. It is recommended to temper at least twice.

A third tempering cycle for the purpose of stress relieving may be advantageous.

1st tempering approx. 30°C (86°F) above maximum secondary hardness.

2nd tempering to desired working hardness.


The tempering chart shows average tempered hardness values.

3rd for stress relieving at a temperature 86 to 122°F (30 - 50°C) below highest tempering temperature.

Recommended tempering temperature range is indicated by the blue area in the chart.

Hardening temperature: 1050°C (1922°F)
Specimen size: square 50 mm

Hot strength chart

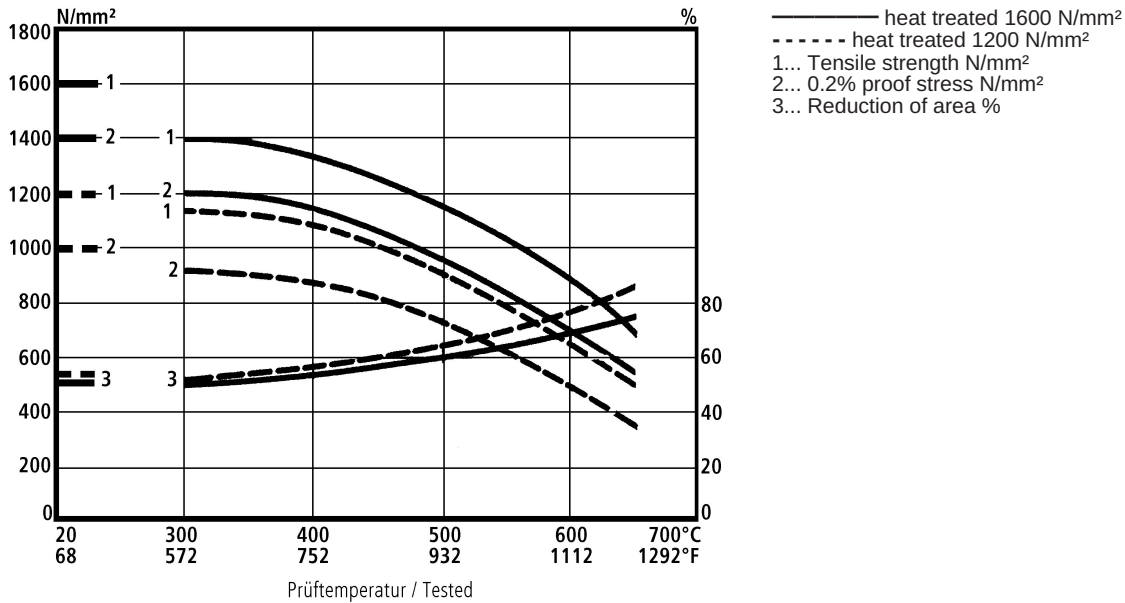

Physical Properties

| | |
|-----------------------------------------|------|
| Temperature (°C) | 20 |
| Density (kg/dm³) | 7.9 |
| Thermal conductivity (W/(m.K)) | - |
| Specific heat (kJ/kg K) | 0.46 |
| Spec. electrical resistance (Ohm.mm²/m) | 0.5 |
| Modulus of elasticity (10³N/mm²) | 215 |

Thermal Expansions between 20°C | 68°F and ...

| Temperature (°C) | 100 | 200 | 300 | 400 | 500 | 600 | 700 |
|----------------------------------------------|------|-----|------|------|------|-----|------|
| Thermal expansion (10 ⁻⁶ m/(m.K)) | 11.5 | 12 | 12.2 | 12.5 | 12.9 | 13 | 13.2 |

If other available product variants are listed in addition to long products, please note that these may differ in terms of melting process, technical data, delivery and surface condition as well as available product dimensions. For mandatory technical specifications, other requirements and dimensions, please contact our regional voestalpine BÖHLER sales companies. The data contained in this brochure is merely for general information and therefore shall not be binding on the company. We may be bound only through a contract explicitly stipulating such data as binding. Measurement data are laboratory values and can deviate from practical analyses. The manufacture of our products does not involve the use of substances detrimental to health or to the ozone layer.

voestalpine BÖHLER Edelstahl GmbH & Co KG

Mariazeller Straße 25
 8605 Kapfenberg, AT
 T. +43/50304/20-0
 E. info@bohler-edelstahl.at
<https://www.voestalpine.com/bohler-edelstahl/de/>