

# OȚELURI PENTRU SCULE PENTRU LUCRU LA CALD

## Application Segments

Lucrări la cald

## Available Product Variants

Long Products\*

Open Die Forgings

\* Datele prezentate se referă exclusiv la produsele lungi. Vă rugăm să respectați explicațiile detaliate de la sfârșitul fișei tehnice (pdf).

## Product Description

BÖHLER W720 VMR is not a classic hot work tool steel, but an ultra-high strength maraging steel. Compared to quenched and tempered steels, the material generates its high strength not through a hardened and tempered martensitic structure with a high carbon content and secondary hardening carbides, but through the precipitation of intermetallic phases from a tough nickel martensitic matrix. BÖHLER W720 VMR corresponds to material number 1.6358 (X2NiCoMoTi18-9-5) and has proven to be ideally suited for many tool steel applications in cold and hot work (e.g., for extrusion stems) up to 450 °C.

## Process Melting

VIM + VAR

## Applications

- > Extrudare
- > Turnare prin injecție
- > Elemente de fixare, șuruburi, piulițe
- > Driveshafts
- > Turnare sub presiune înaltă
- > Inginerie mecanică

## Technical data

Material designation		
1.6358	SEL	
K93120	UNS	

## Chemical composition (wt. %)

C	Si	Mn	Mo	Ni	Co	Ti	Al
≤ 0,030	≤ 0,10	≤ 0,10	5.00	18.50	9.00	0.70	0.10

## Delivery condition

### Soluție recoaptă

Hardness (HB)	max. 353
---------------	----------

### Soluție recoaptă + precipitare întărită

Ultimate tensile strength (UTS) (MPa)	min. 1900
---------------------------------------	-----------

## Heat treatment


### Recoacere în soluție

Temperature	820 °C	1 hour air, gas
-------------	--------	-----------------

### Întărirea prin precipitare

Temperature	430 °C	3 hours / air 1720 to 1870 N/mm <sup>2</sup>
Temperature	480 °C	3 hours / air 1860 to 2000 N/mm <sup>2</sup>

## Ageing chart

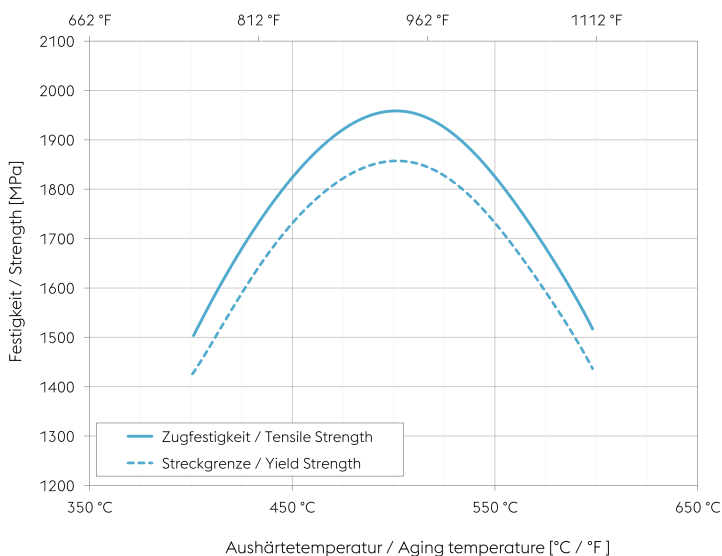

### Aging:

Solution annealed 820°C (1508°F) / 1 hour / air  
Aging time: 3 hours

## Physical Properties

<b>Temperature (°C)</b>	<b>20</b>
Density (kg/dm <sup>3</sup> )	8.2
Thermal conductivity (W/(m.K))	14
Specific heat (kJ/kg K)	0.46
Spec. electrical resistance (Ohm.mm <sup>2</sup> /m)	0.4
Modulus of elasticity (10 <sup>3</sup> N/mm <sup>2</sup> )	193

## Thermal Expansions between 20°C | 68°F and ...

Temperature (°C)	100	200	300	400	500	600
Thermal expansion (10 <sup>-6</sup> m/(m.K))	10.2	10.8	11	11.4	11.8	11.8

If other available product variants are listed in addition to long products, please note that these may differ in terms of melting process, technical data, delivery and surface condition as well as available product dimensions. For mandatory technical specifications, other requirements and dimensions, please contact our regional voestalpine BÖHLER sales companies. The data contained in this brochure is merely for general information and therefore shall not be binding on the company. We may be bound only through a contract explicitly stipulating such data as binding. Measurement data are laboratory values and can deviate from practical analyses. The manufacture of our products does not involve the use of substances detrimental to health or to the ozone layer.

**voestalpine BÖHLER Edelstahl GmbH & Co KG**

Mariazeller Straße 25

8605 Kapfenberg, AT

T. +43/50304/20-0

E. [info@bohler-edelstahl.at](mailto:info@bohler-edelstahl.at)<https://www.voestalpine.com/bohler-edelstahl/de/>