

ČELICI ZA TOPLI RAD

Segmenti aplikacija

Topli rad

Dostupne varijante proizvoda

Šipkasti proizvodi*

Ploče

Otvoreno kovanje

* Prikazani podaci odnose se isključivo na duge proizvode. Molimo obratite pažnju na detaljna objašnjenja na kraju podatkovne tablice (pdf).

Opis proizvoda

BÖHLER W350 ISOBLOC je materijal proizveden postupkom elektroslag taljenja (ESR) koji je posebno prikladan za uporabu u velikim kalupima za lijevanje i kovanje.

Iako se čelik može klasificirati kao čelik s 5% kroma, kemijski sastav je odabran tako da osigura najbolju moguću sposobnost potpunog kaljenja bez gubitka žilavosti ili otpornosti na toplinske pukotine.

Zahvaljujući tim svojstvima, čelik je savršen izbor za izradu vrlo velikih kalupa za tlačno lijevanje, primjerice za mega- ili giga-lijevanje.

Put taljenja

Zrak otopljen + pretopljen

Karakteristike

- > Žilavost i duktilnost : vrlo visoka
- > Otpornost na habanje : visok
- > Obradivost : vrlo visoka
- > Tvrdća pri visokim temperaturama : visok
- > Mogućnost poliranja : vrlo visoka
- > Toplinska vodljivost : vrlo visoka
- > Mikro čistoća : visok

Korištenje

- > Visokotlačno lijevanje
- > Lijevanje ubrizgavanjem
- > Progresivno kovanje (Hatebur)
- > Kovanje (vruće / poluvruće)
- > Tlačno otvrdnjavanje / vruće oblikovanje
- > Mehanika Inženjerstvo / izrada strojeva Općenito
- > Gravitacijsko / niskotlačno lijevanje
- > Istiskivanje

Technički podaci

Oznaka materijala	Standardi
BÖHLER patent	#207
Market grade	NADCA
E1850	NADCA

Kemijski sastav

C	Si	Mn	Cr	Mo	V	N
0.38	0.20	0.55	5.00	1.80	0.55	def.

Materijal

	Otpornost na toplinu	Vruća žilavost	Otpornost na vruće trošenje	Obradivost u stanju isporuke	Poliranje
BÖHLER W350 ISOBLOC	★★★	★★★★★	★★★	★★★★★	★★★★★
BÖHLER W300 ISOBLOC	★★	★★★★	★★	★★★★★	★★★★★
BÖHLER W300 ISODISC	★★	★★★	★★	★★★★★	★★★
BÖHLER W302 ISOBLOC	★★★	★★★★	★★★	★★★★★	★★★★★
BÖHLER W302 ISODISC	★★★	★★★	★★★	★★★★★	★★★
BÖHLER W303 ISODISC	★★★★	★★★	★★★★	★★★★★	★★★
BÖHLER W320 ISODISC	★★★	★★	★★★	★★★★★	★★★
BÖHLER W360 ISOBLOC	★★★★★	★★★★	★★★★★	★★★★★	★★★★★
BÖHLER W400 VMR	★★	★★★★★	★★	★★★★	★★★★★
BÖHLER W403 VMR	★★★★	★★★★	★★★★	★★★★	★★★★★

Isporuka

Žarenje	
Tvrdoća (HB)	max. 205


Toplinska obrada

Žarenje		
Temperatura	750 do 800 °C	Slow controlled cooling in furnace at a rate of 10 to 20 °C/hr (50 to 68 °F/hr) down to approx. 600 °C (112 °F), further cooling in air.


Ublažavanje stresa		
Temperatura	600 do 670 °C	Slow cooling furnace. To relieve stresses caused by extensive machining, or for complex shapes. Soak for 1 -2 hours after temperature equalisation (in neutral atmosphere).

Stvrdnjavanje i kaljenje		
Temperatura	1,010 do 1,020 °C	Holding time after temperature equalization: 15 to 30 minutes; In order to prevent coarsening of the grain, hardening must be carried out at the recommended temperature. For big dimensions it's recommended to reduce the temperature to 1010 °C (1850 °F); Quenching: oil, salt bath (500 - 550°C [932 - 1022 °F]), air, inert gas in vacuum; After hardening, required tempering treatment to achieve desired working hardness (see tempering chart).

Heat treatment sequence

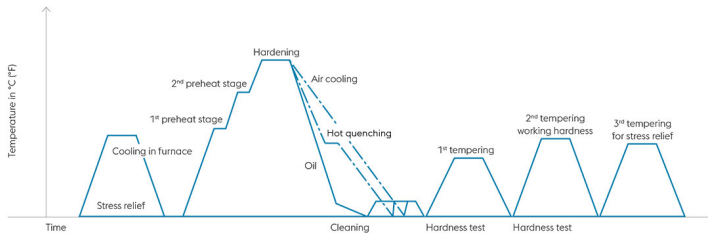

Continuous cooling CCT curves

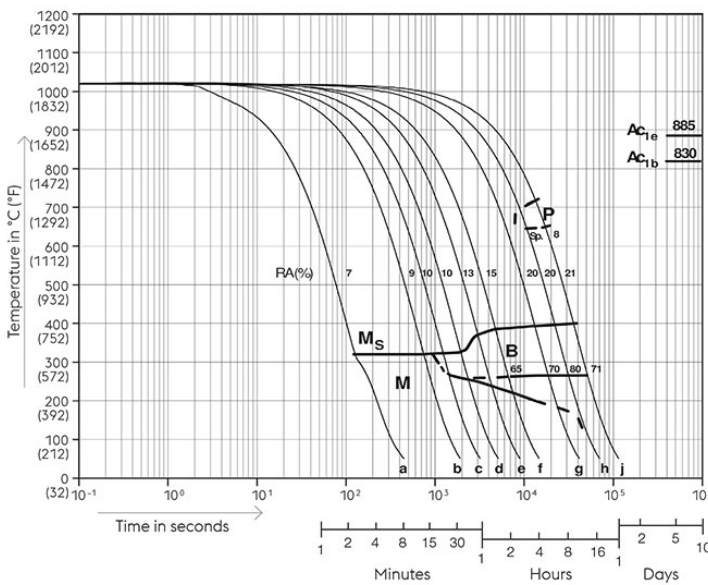


Austenitising temperature: 1020°C (1868°F)
 Holding time: 15 minutes
 5...100 phase percentages
 0.5...180 cooling parameter, i.e. duration of cooling from 800 - 500°C (1472-932°F) in s x 10⁻²

Table:


Sample	λ	HV10	Sample	λ	HV10
a	0,5	630	f	23	478
b	3	616	g	65	497
c	5	606	h	110	454
d	8	606	j	180	459
e	14	517			

Quantitative phase diagram

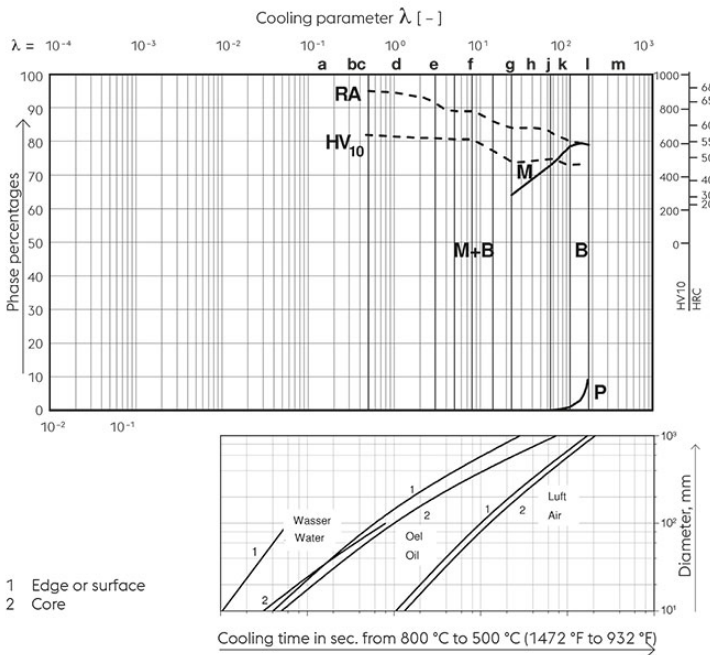

A... Austenite
 B... Bainite
 K... Carbide
 M... Martensite
 P... Pearlite
 RA... Retained austenite

Tempering chart

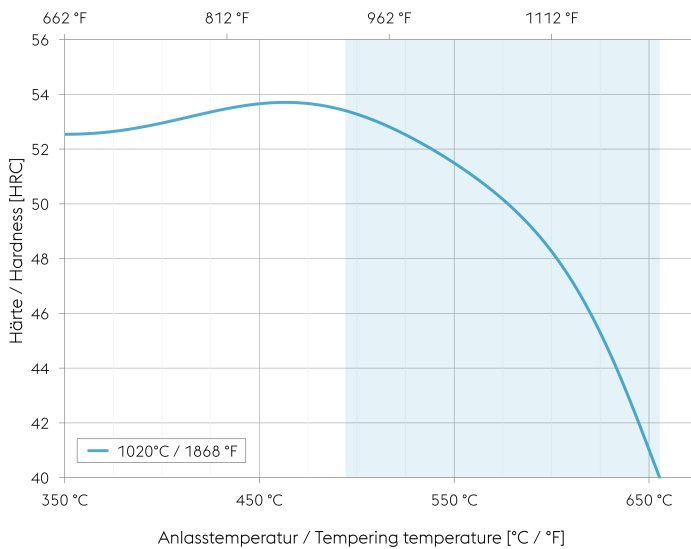

Tempering:

Slow heating to tempering temperature immediately after hardening (time in furnace 1 hour for each 0,787 inch (20 mm) of workpiece thickness but at least 2 hours / cooling in air).

It is recommended to temper at least twice.

A third tempering cycle for the purpose of stress relieving may be advantageous.

1st tempering approx. 86°F (30°C) above maximum secondary hardness.

2nd tempering to desired working hardness.

The tempering chart shows average tempered hardness values.

3rd for stress relieving at a temperature 86 to 122°F (30 to 50°C) below highest tempering temperature.

Recommended tempering temperature range is indicated by the blue area in the chart.

Hardening temperature: 1020°C (1868°F)
 Specimen size: square 20 mm

Fizička svojstva

Temperatura (°C)	20
Gustoća (kg/dm ³)	7.8
Toplinska vodljivost (W/(m.K))	28.8
Specifični toplinski kapacitet (kJ/kg K)	0.46
Spec. Otpornik (Ohm.mm ² /m)	-
Modul elastičnosti (10 ⁹ N/mm ²)	214

Toplinska ekspanzija

Temperatura (°C)	100	200	300	400	500	600	700
Toplinska ekspanzija (10 ⁻⁶ m/(m.K))	11.1	11.9	12.4	12.9	13.2	13.5	13.6

Ako su pored šipkastih proizvoda navedene i druge dostupne varijante proizvoda, imajte na umu da se one mogu razlikovati u pogledu procesa taljenja, tehničkih podataka, stanja isporuke i površinske obrade kao i dostupnih dimenzija proizvoda. Za obvezne tehničke specifikacije, ostale zahtjeve i dimenzije molimo Vas obratite se našim regionalnim voestalpine BÖHLER prodajnim tvrtkama. Informacije u ovom prospektu nisu obvezujuće i ne smatraju se prihvaćenima; umjesto toga, oni su samo za opće informacije. Te su informacije obvezujuće samo ako su izričito postavljene kao uvjet u ugovoru sklopljenom s nama. Mjerni podaci su laboratorijske vrijednosti i mogu se razlikovati od praktičnih analiza. U proizvodnji naših proizvoda ne koriste se tvari štetne za zdravlje ili ozon.

voestalpine BÖHLER Edelstahl GmbH & Co KG

Mariazeller Straße 25

8605 Kapfenberg, AT

T. +43/50304/20-0

E. info@bohler-edelstahl.at

<https://www.voestalpine.com/bohler-edelstahl/de/>

voestalpine

ONE STEP AHEAD.